



中国认可
国际互认
检测
TESTING
CNAS L11342



TEST REPORT

Performance Tests for Synthetic Surfaces Intended for Multi-Sports Facilities
According to EN 14877:2013 Synthetic surfaces for outdoor sports areas - Specification

Interlocking Sports Flooring

Hebei Enlio Sports Goods Co., Ltd

LABORATORY TEST REPORT N°: LSA-R24553-A1

Test Date: 2024.09.23-2025.01.17

Report Date: 2025.02.07

This report contains 5 pages in total.

This report is unique and made up of pages with the same report number and consecutive page numbers.

This report is invalid without the laboratory's stamp.

Without the laboratory's prior written approval, this report must be used as a whole and cannot be partially duplicated.

The laboratory reserves the right to prosecute any party that will alter or falsify this report.

Unless otherwise stated, this report's results refer only to the samples received and tested by the laboratory.



Guangzhou LABOSPORT Co., Ltd.

1/F, Building C, No.1, Huan Bao 3rd Road, Xintang Town, Zengcheng District, Guangzhou, Guangdong, China

Email: asia@labosport.com

Office: +86-20-8190 0714

Page 1 of 5

1. CLIENT DETAILS

Company: Hebei Enlio Sports Goods Co., Ltd

Address: Room 10-409, No.266 Tianshan St., Shijiazhuang City, Hebei Province, China

Contact: 宜旭旭, Tel: +86 18832131031, E-mail: 773400416@qq.com

Date of order: 2024.09.20

2. TESTING PROGRAM

Guangzhou Labosport has been commissioned by **Hebei Enlio Sports Goods Co., Ltd** to carry out laboratory tests on the sport flooring named **Interlocking Sports Flooring**.

Technical requirements criteria considered in this report refer to the standard:

-EN 14877:2013 Synthetic surfaces for outdoor sports areas - Specification - Table 3 - Synthetic surfaces intended for multi-sports facilities

-The following tests have been carried out on the surface in accordance with the following standard/test methods:

-Friction.....	EN 13036-4:2011 (CEN rubber & Dry/Wet)
-Shock Absorption.....	EN 14808:2005
-Vertical deformation.....	EN 14809:2005
-Vertical ball rebound.....	EN 12235:2013 (using a basketball)
-Water permeability.....	EN 12616:2022 Part 1 Method A
-Resistance to wear.....	ISO 5470-1:2016 (using H18 wheels with a 1 kg load)
-Resistance to UVA.....	EN 14836:2018 (method 1)
-Colour loss.....	EN ISO 20105-A02
-Tensile properties.....	EN 12230:2022 Method 1
-Accelerated ageing by hot air.....	EN 13817:2004
-Accelerated ageing by hot water.....	EN 13744:2004
-Thickness.....	EN 1969:2000

Dimensions of the tested samples conform to the testing standards.






Samples were tested in accordance with the client's instructions (installation conditions, laying type).


-Tests were realized in laboratory where temperature and humidity are controlled.

-The tests conditions were:

Temperature (°C)	23 °C ± 2 °C
Air humidity (%)	50 % ± 5%

3. SAMPLES DETAILS (client declaration)

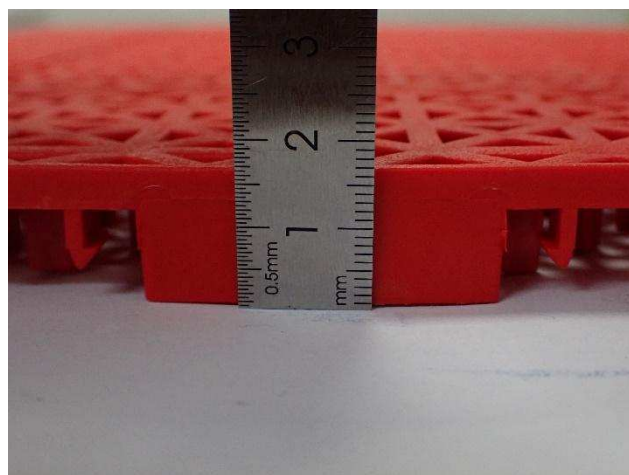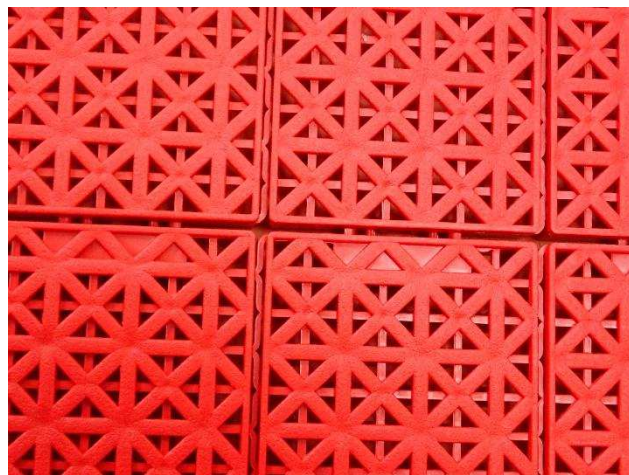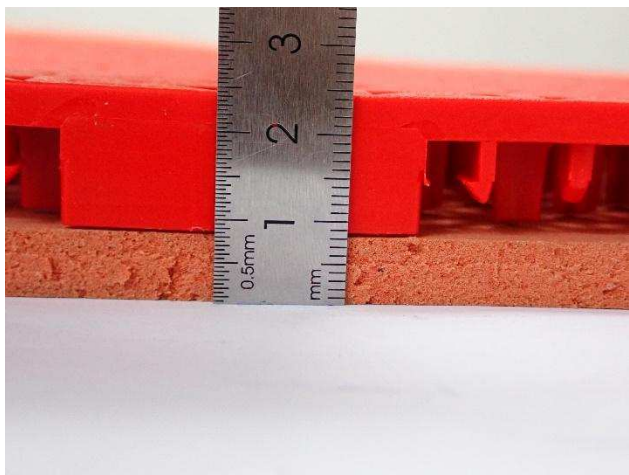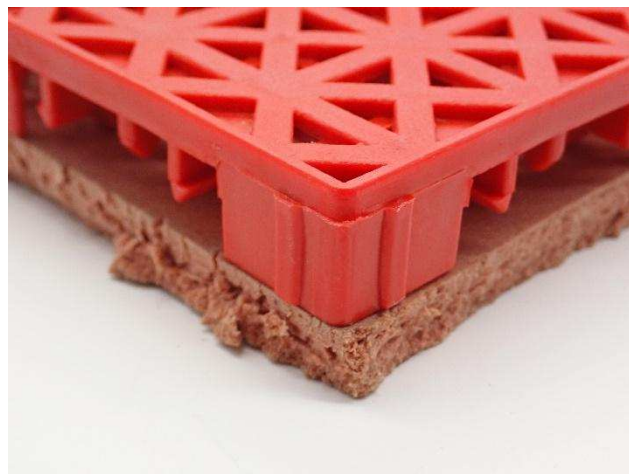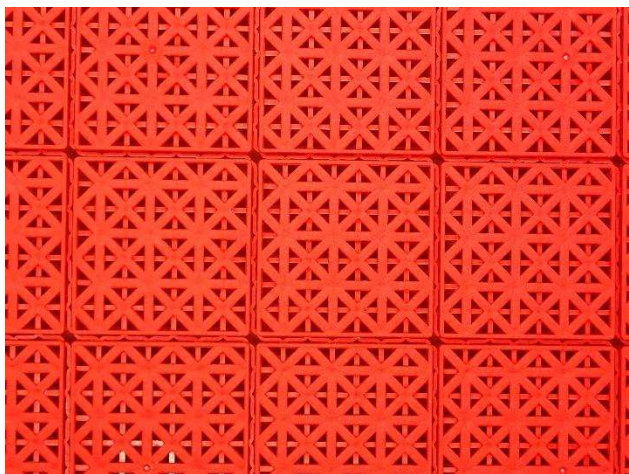

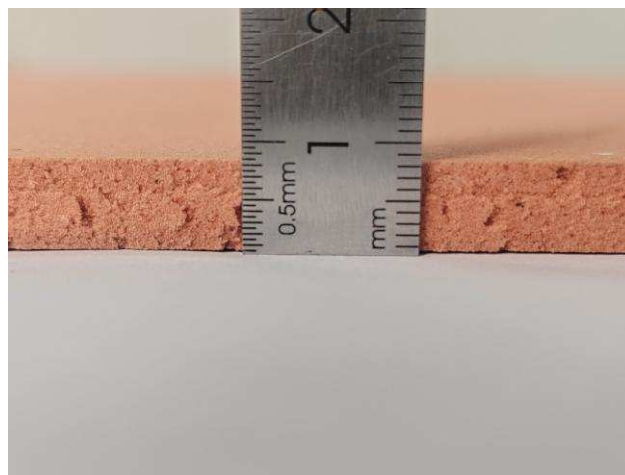

Product name	Interlocking Sports Flooring ^①
Sport Facilities	Multi-sports-facilities ^①
Thickness	Interlocking 15.8mm; Red Shockpad 8mm ^①
Internal Reference	S24553-1/S24553-2

^① Above product declaration is provided and confirmed by Hebei Enlio Sports Goods Co., Ltd.

4. TESTS RESULTS

Properties	Methods	Units	Conditions	Results	Requirements
Friction	EN 13036-4 CEN Rubber	-	Dry, 23±2 °C	90	80 – 110
			Wet, 23±2 °C	30 ^②	55 – 110
Shock Absorption	EN 14808	%	Dry, 23±2 °C	43	25 – 75 (Classification SA 35 to 44)
			After A/W Ageing ^③ , 23±2 °C	44	
Vertical deformation	EN 14809	mm	Dry, 23±2 °C	4.2	≤ 6
Vertical ball rebound	EN 12235	%	Dry, 23±2 °C Basketball	92	≥ 97
Water permeability	EN 12616	mm/h	23±2 °C	Impermeable ^④	≥ 150
Resistance to wear	ISO 5470-1	g	Unaged, 23±2 °C	0.103	≤ 4.0 of mass loss between 500 and 1,500 cycles
			After Ageing UVA ^⑤	0.120	
Colour change	EN ISO 20105-A02	-	After Ageing UVA ^⑤	4	≥ 3
Tensile properties	EN 12230	Mpa	Unaged, 23±2 °C	0.47 ^⑥	≥ 0.40
			After A/W Ageing ^③ , 23±2 °C	0.48 ^⑥	
Elongation at break	EN 12230	%	Unaged, 23±2 °C	47 ^⑥	≥ 40
			After A/W Ageing ^③ , 23±2 °C	45 ^⑥	
Thickness-Top layer	EN 1969 (method A)	mm	23±2 °C	15.8	Total ≥ 7
Thickness-Bottom layer	EN 1969 (method A)	mm	23±2 °C	8.0	

^② Not suitable for wet conditions.

^③ After A/W Ageing-After accelerated ageing by hot air and hot water.

^④ Note: the top layer made of interlocking tiles is a hollow design with good horizontal drainage capacity.

^⑤ Test according to EN 14836:2018 (Method 1).

^⑥ Interlocking and shockpad combined for testing.

REPORTED BY:



Xiong Yihai
Laboratory Manager

APPROVED BY:



Jiuling Zhou
TECHNICAL MANAGER

~~~~~The End~~~~~